

# Anion Vacancy Driven Magnetism in Superconducting $\alpha$ -FeSe $_{1-x}$

K.-W. Lee<sup>1,2</sup>, V. Pardo,<sup>1,3</sup> and W. E. Pickett<sup>1</sup>

<sup>1</sup>*Department of Physics, University of California, Davis, CA 95616, USA*

<sup>2</sup>*Department of Display and Semiconductor Physics, Korea University, Jochiwon, Chungnam 339-700, Korea*

<sup>3</sup>*Departamento de Física Aplicada, Facultad de Física, Universidad de Santiago de Compostela, E-15782 Campus Sur s/n, Santiago de Compostela, Spain*

(Dated: August 12, 2008)

To study the microscopic electronic and magnetic interactions in the substoichiometric iron chalcogenide FeSe $_{1-x}$  which is observed to superconduct at  $x \approx \frac{1}{8}$  up to  $T_c=27$  K, we use first principles methods to study the Se vacancy in this system. The vacancy forms an immobile strong magnetic polaron in nearly magnetic FeSe, which for the ordered  $x=\frac{1}{8}$  alloy leads to half metallic conduction. Similar magnetic clusters are obtained for FeTe $_{1-x}$  and for BaFe $_2$ As $_2$  with an As vacancy, but both are not half metallic. Based on fixed spin density results, we suggest the low energy excitations in FeSe $_{1-x}$  are antiparamagnon-like with short correlation length.

PACS numbers: 74.70.-b, 74.25.Jb, 75.25.+z, 71.20.Be

The discovery of superconductivity,[1] now up to 55 K in the LaFeAsO class of compounds, followed by  $T_c$  of nearly 30 K in the BaFe $_2$ As $_2$  class with the same active conducting Fe $_2$ As $_2$  layer has caused tremendous excitement. A competition between superconductivity and magnetism is very evident, and the assortment of phenomena, concepts, and proposed models is leading to a murkiness that is reminiscent of the heyday of high temperature superconducting cuprates. There is a serious need to identify and address relatively straightforward questions, in addition to broader investigations to compare and contrast all the  $\mathcal{R}$ FeAsO materials ( $\mathcal{R}$ =rare earth) to identify trends that might provide a clue. The new system, FeSe, with only two atoms, is structurally simpler and provides more direct questions. Although many samples are two phase and are not always fully characterized, this system seems to be non-magnetic and non-superconducting at stoichiometry, and is magnetic and clearly superconducting [2, 3, 4, 5, 6] at Se substoichiometry FeSe $_{1-x}$ .

FeSe can be substoichiometric on either sublattice and contains two major phases ( $\alpha$  and  $\beta$ ). The PbO-type  $\alpha$ -FeSe $_{1-x}$  compound is the one of current interest and has been studied extensively for its spintronics-related magnetic properties by Zhen and coworkers,[7, 8, 9, 10] who concluded from observed hysteresis a ferromagnetic state in the non-stoichiometric phase, but a nonmagnetic state in the stoichiometric phase. Very recently, Hsu *et al.* reported superconductivity with  $T_c = 8$  K, at  $x = 0.12$  and 0.18.[2] Subsequently,  $T_c$  has been raised rapidly up to 27 K at pressure  $P = 1.48$  GPa,[3, 4] clearly putting FeSe $_{1-x}$  in the high  $T_c$  category with iron pnictides having similar band filling. Margadonna *et al.* confirmed  $T_c \sim 14$  K at  $x = 0.08$  at am-

TABLE I: Optimized structure for a  $2 \times 2$  supercell with a Se vacancy (space group:  $P4mm$ , No. 99), *i.e.* Fe $_8$ Se $_7$ . The order of Fe-Fe distances for the relaxed structure is Fe1-Fe1, Fe2-Fe2, and Fe1-Fe2. Fe1 means Fe atoms near a Se vacancy. Note that this structure is optimized in ferromagnetic state.

	Unrelaxed			Relaxed			
	$x$	$y$	$z$	$x$	$y$	$z$	
Fe1	$4e$	0	0.25	0	0	0.2520	0.2375
Fe2	$4f$	0.5	0.25	0	0.5	0.2637	0.2350
Se1	$2c$	0.5	0	0.7628	0.5	0	0.9950
Se2	$4d$	0.25	0.25	0.2372	0.2481	0.2481	0.4795
Se3	$1a$	0	0	0.7628	0	0	0.0020
bond	Fe-Se: 2.28			Fe1(Fe2)-Se: 2.33(2.29)			
length (Å)	Fe-Fe: 2.66			Fe-Fe: 2.52, 2.68, 2.73			

bient pressure.[4] Fang *et al.* investigated isovalent Fe(Se $_{1-y}$ Te $_y$ ) $_{0.82}$ ,[5] finding  $y$ -dependent  $T_c$  in the range of 8–14 K with maximum at  $y \approx 0.6$ , dipping to zero at  $y = 1$ . Notably, temperature dependent susceptibility measurements show an anomaly around 100 K, indicating a peculiar and not yet understood magnetic instability.[2, 5] Hence, the competition between superconductivity and magnetism observed in iron pnictides is clearly extended to these iron chalcogenides, and the current picture seems to be that superconductivity arises in a phase with strong magnetic character. Here we focus on a crucial feature: Se vacancies are necessary for producing the high temperature superconducting state, so what is the character of this defect?

In the tetragonal phase  $\alpha$ -FeSe with PbO (B10) structure (space group:  $P4/nmm$ , No. 129), Fe and Se atoms lie at  $2a$  sites (0,0,0) and at  $2c$  sites ( $0, \frac{1}{2}, z$ ), respectively. The Fe $_2$ Se $_2$  layers have the same struc-

ture as in LaFeAsO and BaFe<sub>2</sub>As<sub>2</sub>. The experimental lattice parameters  $a=3.7693$  Å and  $c=5.4847$  Å, which are reported recently by Hsu *et al.* at  $x=0.12$ , [2] are used in our calculations. The internal parameter  $z = 0.2372$  is optimized by energy minimization within the local density approximation (LDA).

Since the superconductivity has been observed around  $x = 0.12$  at ambient pressure, we have used a  $2 \times 2$  supercell containing 8 formula units. In this supercell, a Se vacancy represents the  $x = 0.125$  phase, well within the superconducting regime. In this phase, this supercell contains two types of Fe atoms, one being adjacent to the Se vacancy (Fe1) and the other farther away (Fe2). As shown in our optimized structure given in Table I, the main effect of the Se vacancy on the structure is to shift Fe1 atoms toward the vacant site, whereas Fe2 atoms are affected little. The changes in interatomic distance are  $-0.14$  Å for Fe1–Fe1,  $+0.07$  Å for Fe1–Fe2, and  $+0.05$  Å for Fe1–Se.

Two all-electron full-potential codes, FPLO-7 [11, 12] and WIEN2k [13] based on the augmented plane wave+local orbitals (APW+lo) method, [14] have been used in these calculations, with consistent results. The Brillouin zone was sampled with regular dense mesh containing up to 720 irreducible  $k$  points. Using WIEN2k with the Perdew-Wang LDA exchange-correlation functional, [15] the atomic positions in the  $2 \times 2$  supercell with one Se vacancy were optimized until forces were smaller than 2 mRy/a.u.. For WIEN2k, local orbitals were added to gain flexibility in dealing with semicore states, Fe  $3p$  and Se  $3d4s$ . The basis size was determined by  $R_{mt}K_{max}=6$ . Atomic radii used were 2.21 a.u. for Fe and 1.96 a.u. for Se.

*Stoichiometric phase.* All attempts to obtain either ferromagnetic (FM) or antiferromagnetic (AFM) states led only to nonmagnetic (NM) solution. Even in the fixed spin moment calculations, no (meta)stable FM state is obtained. The nonmagnetic ground state at  $x = 0$  is consistent with experimental observations. [10] Subedi *et al.* [16] reported an AFM ground state with a very small stabilization energy; this result is not in conflict since energies and moments are known to be very sensitive to structural and computational details. These two results taken together indicate FeSe is very near a magnetic critical point.

As seen in other superconductors containing FeAs layers, a transition from tetragonal to a low temperature orthorhombic structure has been observed around  $T = 70$  K. [2, 4] As expected from the tiny changes in crystal structures, the calculated change in electronic structures is slight. We will address only the tetragonal phase here.

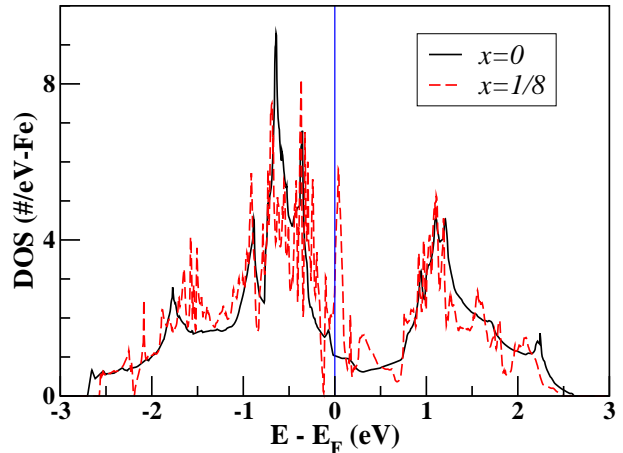


FIG. 1: (color online) Total densities of states (DOSs) per Fe (both spins), for nonmagnetic  $x=0$  and nonmagnetic  $x = \frac{1}{8}$  in the optimized structures, in the regime of Fe  $3d$  states. Note that the Fermi level  $E_F$  of  $x = \frac{1}{8}$  lies on steep side of a sharp peak, promoting a stable magnetic state.  $N(E_F)$  of  $x = \frac{1}{8}$  at  $E_F$  is 3.07 states/eV per one Fe, which is about 3 times larger than that of  $x = 0$ .

The main difference in the band structure of FeSe [16] with respect to iron pnictide compounds with similar structure occurs along the  $\Gamma - Z$  line ( $k_z$  direction). FeSe has a similar band structure to BaFe<sub>2</sub>As<sub>2</sub> [17], with a flat band (a  $d$  orbital lying in the  $xy$ -plane with a large Fe-Fe hopping integral) (at  $-20$  meV) just below  $E_F$ , whereas this band lies above  $E_F$  in LaOFeAs [18], FeTe [16] and LiFeAs [17]. As might be expected, the FSs are less two-dimensional in FeSe than in iron pnictide compounds, which have another layer of atoms between FePn layers. The FSs, shown already by Subedi *et al.*, [16] consist of two  $\Gamma$ -centered hole cylinders, which contain 0.07 and 0.04 holes per a Fe respectively, and two compensating  $M$ -centered electron cylinders with more dispersion along the  $k_z$  direction.

Figure 1 shows the total density of states for  $x = 0$  compared with that for  $x = 0.125$ . The density of states  $N(E_F)$  for  $x = 0$  is small, 25% less than the value for LaFeAsO and providing no tendency for a FM instability. However, there is a van Hove singularity at  $-50$  meV, which is absent in the Fe-As superconductors. A difference compared to Fe-As compounds is the hybridization gap at  $-3$  eV that suggests strong Fe-Se hybridization, consistent with about 5% smaller Fe-Se distance in this compound than Fe-As distance in either LaFeAsO or BaFe<sub>2</sub>As<sub>2</sub>. The Se  $p$  states also lie somewhat lower than the As  $p$  states.

*Effect of a Se vacancy.* This Se vacancy cannot

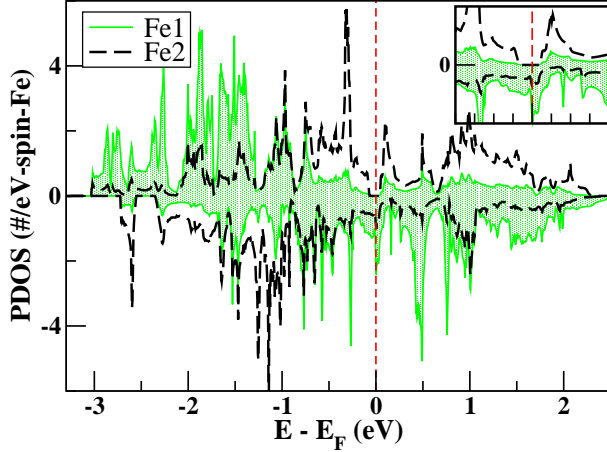


FIG. 2: (color online) Fe atom-projected densities of state (PDOSs) of magnetic  $x = \frac{1}{8}$  in the regime of Fe 3d states. The vertical line indicates  $E_F$ , set to zero, which passes through a peak in the minority and nearly bisects the gap of  $\sim 0.1$  eV in the majority. *Inset:* Blowup PDOS in the range of  $-0.4$  to  $0.4$  eV, clearly showing a gap in the majority channel.

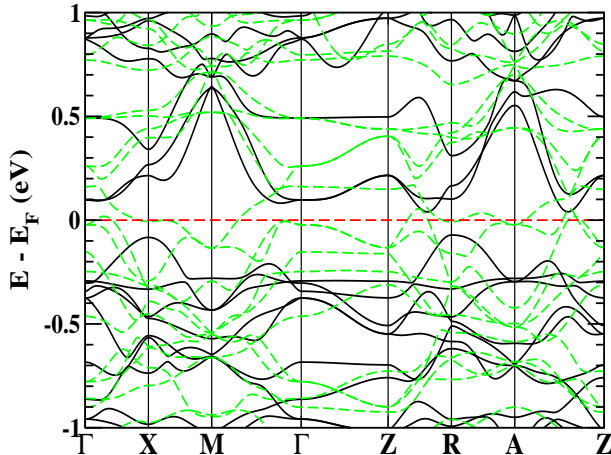


FIG. 3: (color online) Blowup band structure of magnetic  $x = \frac{1}{8}$ , showing half-metallicity with total spin moment of  $0.5 \mu_B$  per Fe, near  $E_F$  which is set to zero.

be treated well by the virtual crystal approximation, which we have confirmed by calculations, thus necessitating a supercell treatment of the actual vacancy. For  $x = 0.125$ , we find that a strong magnetic state centered on the vacancy is stabilized (see below). This relaxed immobile magnetic polaron, with structure given in Table I, gains 32 meV/Fe by structural relaxation. Disregarding magnetism, both structures are nearly degenerate. Thus difference reflects important magnetostructural coupling, as already

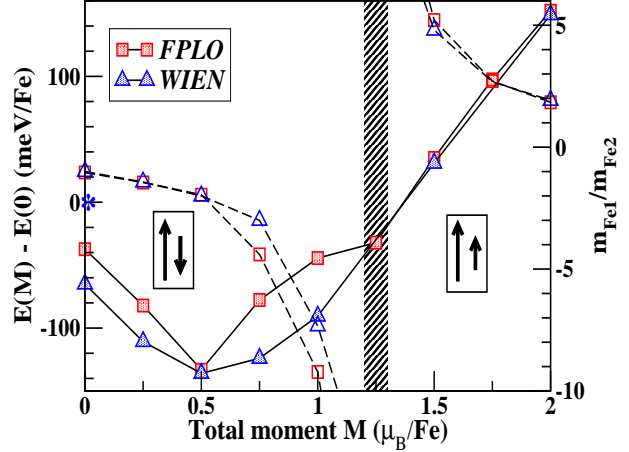


FIG. 4: (color online) Total energy differences (solid lines, scale on the left axis) and ratio of local moments on Fe ions (dashed lines, scale on the right axis) versus fixed spin moment, using FPLO and WIEN2k. For  $M \approx 0.75$ – $1 \mu_B$ , two distinct states can be found. The dashed area is a boundary separating regimes of antiparallel and parallel spin moments (at the boundary, Fe2 has nearly zero moment), described by arrows. The symbol \* at  $M=0$  denotes nonmagnetic state, which has zero energy  $E(0)$  in this plot. The  $M=0$  state at  $-65$  meV has compensating moments on Fe1 and Fe2 of magnitude  $\sim 1.9 \mu_B$ . (For details, see text.)

found for LaFeAsO,[18] and dependence of optimized structure on magnetic states is observed commonly in the FeAs-based superconductors,[19, 20] which have large calculated spin moment. In this relaxed structure, the magnetization energy (energy difference between NM and FM) is 133 meV/Fe, one-third larger than in the unrelaxed structure and reflecting a very strongly magnetic cluster.

Now we will address the unusual properties of the magnetic state. The most interesting point is that the two types of Fe ions are aligned antiparallel: Fe1 with  $2.14 \mu_B$  and Fe2 with  $-1.10 \mu_B$  in the relaxed structure. This distribution of Fe  $d$  states of each spin can be observed in the atom-projected densities of states given in Fig. 2. The total moment is  $0.5 \mu_B/\text{Fe}$ , and in addition this ordered system is half-metallic, as shown clearly in the band structure given in Fig. 3. In the unrelaxed structure each Fe ion has smaller moment in magnitude by  $0.25 \mu_B$ , although the total moment remains unchanged. The Se vacancy leads to creation of antialigned spin moments rather than any identifiable charge difference between Fe ions.

*Fixed spin moment studies.* One may ask: how stable is the antialigned spin state? Fixed spin moment calculations[21] in the  $\text{Fe}_8\text{Se}_7$  compound are used to investigate this question. Results can be seen

in Fig. 4, which shows the clear energy minimum around the half-metallic solution with  $0.5 \mu_B/\text{Fe}$  ( $4 \mu_B$  per magnetic cluster). Note that the  $E(M)$  curve is not smooth at a point of half metallicity[22] where a substantial range of "applied field" leads to the same unchanging moment. For total moment  $M=0$ , two solutions are found: the antialigned spin state with net zero moment and the simple nonmagnetic state. The antialigned state has lower energy by 65 (37 in FPLO) meV/Fe than the nonmagnetic state, but higher energy by 71 meV/Fe than the half metallic state. However, the nonmagnetic solution is more stable than any solution with parallel aligned spins. These results indicate that parallel spins are strongly antagonistic for this magnetic cluster.

For antialigned spin states, the difference in total energy between the two codes used here is associated with different local moments on Fe ions. At  $M=0$  and  $0.25 \mu_B$ , the moment of Fe1 obtained in WIEN2k is about 15% larger than in FPLO, though the ratio of Fe local moments is nearly identical. These differences probably reflect the sensitivity of  $\text{FeSe}_{1-x}$ —the softness of its magnetism—to small computational details rather than representing distinct magnetic states. Additionally, changing the total moment for the antialigned spin states, the Fe1 moment is insensitive, with only a maximum change of 10%, whereas the Fe2 moment varies rapidly. For such a system, low energy excitations involve essentially little change in the Fe1 magnetic moment.

To check the robustness of this vacancy induced magnetic cluster, we carried out analogous calculations for  $\text{FeTe}_{1-x}$  and  $\text{BaFe}_2\text{As}_2$ . A similar structural relaxation was performed for  $\text{FeTe}_{0.875}$  as in  $\text{FeSe}$ ,[23] and an As vacancy in  $\text{BaFe}_2\text{As}_2$ , *i.e.*  $\text{Ba}_4\text{Fe}_8\text{As}_7$ . [24] For  $\text{BaFe}_2\text{As}_{1.75}$  and  $\text{FeTe}_{0.875}$ , the relaxation and magnetic cluster are similar although the final states are not half metallic, with total moment of  $0.7 \mu_B/\text{Fe}$  and  $0.42 \mu_B/\text{Fe}$ , respectively. These magnetic states are favored energetically over the nonmagnetic state by about 160 meV/Fe for  $\text{BaFe}_2\text{As}_{1.75}$  and 175 meV/Fe for  $\text{FeTe}_{0.875}$ .

Now we consider the broader context. Magnetism in superconducting samples, and its possible connection to superconductivity, is one of the primary issues in iron-pnictide superconductivity, and our calculations establish that Se (or Te, or As) vacancies promote strong magnetic clusters surrounding the vacancy. Superconductivity occurs only in substoichiometric samples, and we obtain strong magnetic behavior only around Se vacancies. Our fixed spin moment results indicate the low energy excitations will involve fluctuations in the magnitude of the next neighbor Fe spin (relative to the vacancy), while the near neighbor spin remains rigid and antialigned. The character of this excitation is antiparamagon-like but with short correlation length, a scenario that also seems relevant for the iron pnictide superconductors.

In the superconducting  $\text{FeSe}_{0.88}$  materials there is a magnetic transition characterized by a sharp upturn in the susceptibility (apparently also with a structural aspect) near 105 K, followed by another transition at 75 K where the susceptibility abruptly returns to its higher temperature value.[2, 5] These anomalies have not been discussed much yet, but the strong magnetic character, and the difference in field-cooled and zero-field-cooled susceptibility at lower temperature may be reflecting complex cluster-glass behavior arising from the immobile but interacting magnetic defects that we have studied. The appearance of superconductivity in a disordered magnetic system such as this provides strong justification for further study of the physics of the  $\text{FeSe}_{1-x}$  system.

We acknowledge S.-G. Lee for useful discussion about samples and S. Lebègue for useful communications. This research was supported by Korea University Grant No. K0718021 (K.W.L.), Universidad de Santiago de Compostela (V.P.), and DOE Grant DE-FG03-01ER45876 (W.E.P.), and the work benefitted from interactions within DOE's Computational Materials Science Network.

---

[1] Y. Kamihara, T. Watanabe, M. Hirano, and H. Hosono, *J. Am. Chem. Soc.* **130**, 3296 (2008).  
[2] F.-C. Hsu *et al.*, arXiv:0807.2369 (2008).  
[3] Y. Mizuguchi *et al.*, arXiv:0807.4315 (2008).  
[4] S. Margadonna *et al.*, arXiv:0807.4610 (2008).  
[5] M.H. Fang *et al.*, arXiv:0807.4775 (2008).  
[6] K.-W. Yeh *et al.*, arXiv:0808.0474 (2008).  
[7] Q.J. Feng *et al.*, *Appl. Phys. Lett.* **88**, 012505 (2006).  
[8] K.W. Liu *et al.*, *Appl. Phys. Lett.* **90**, 262503 (2007).

[9] X.J. Wu *et al.*, *Appl. Phys. Lett.* **90**, 112105 (2007).  
[10] X.J. Wu *et al.*, *J. Appl. Phys.* **103**, 113501 (2008).  
[11] K. Koepf and H. Eschrig, *Phys. Rev. B* **59**, 1743 (1999).  
[12] FPLO-5 has been used partially to consider the virtual crystal approximation (VCA) that has not been implemented in FPLO-7, yet. Valence orbitals included Fe  $3s3p4s4p3d$  and Se  $3p4s4p3d$  in FPLO-5.  
[13] K. Schwarz and P. Blaha, *Comp. Mat. Sci.* **28**, 259 (2003).  
[14] E. Sjöstedt, L. Nördstrom, and D. J. Singh, *Solid*

- State Commun. **114**, 15 (2000).
- [15] J. P. Perdew and Y. Wang, Phys. Rev. B **45**, 13244 (1992).
- [16] A. Subedi *et al.*, arXiv:0807.4312 (2008)
- [17] D. J. Singh, arXiv:0807.2643 (2008).
- [18] Z.P. Yin *et al.*, Phys. Rev. Lett. **101**, 047001 (2008).
- [19] I. I. Mazin, M. D. Johannes, arXiv:0807.3737 (2008).
- [20] T. Yildirim, arXiv:0807.3936 (2008).
- [21] K. Schwarz and P. Mohn, J. Phys. F:Met. Phys. **14**, L129 (1984).
- [22] K.-W. Lee and W. E. Pickett, Phys. Rev. B **77**, 115101 (2008).
- [23] The experimental lattice parameters[6]  $a=3.819$  Å and  $c=6.250$  Å were used.
- [24] The lattice parameters[25]  $a=3.9625$  Å and  $c=12.0168$  Å were used for the optimization. In the space group  $P4/mmm$  (No.123), atomic positions are Fe1  $8s$  (0,0.2277,0.2561), Fe2  $8t$  (0.2506, $\frac{1}{2}$ ,0.2522); As1  $4i$  (0, $\frac{1}{2}$ ,0.6556), As2  $2h$  ( $\frac{1}{2}$ , $\frac{1}{2}$ ,0.6536), As3  $8r$  (0.2526,0.2526,0.1569); Ba1  $1a$  (0,0,0), Ba2  $2f$  (0, $\frac{1}{2}$ ,0.), Ba3  $1c$  ( $\frac{1}{2}$ , $\frac{1}{2}$ ,0), Ba4  $4k$  (0.2548, 0.2548, $\frac{1}{2}$ ).
- [25] M. Rotter *et al.*, Phys. Rev. B **78**, 020503(R) (2008).